

Performance based design of reinforced concrete beams under impact

S. Tachibana¹, H. Masuya², and S. Nakamura³

¹Hokukon Co., Ltd., Fukui, Japan

²Faculty of Environmental Design, Institute of Science and Engineering, Kanazawa University, Kanazawa, Japan

³Nihon Samicon Co., Ltd., Niigata, Japan

Received: 14 January 2009 – Revised: 21 April 2010 – Accepted: 7 May 2010 – Published: 1 June 2010

Abstract. The purpose of this research is to collect fundamental data and to establish a performance-based design method for reinforced concrete beams under perpendicular impact load.

Series of low speed impact experiments using reinforced concrete beams were performed varying span length, cross section and main reinforcement.

The experimental results are evaluated focusing on the impact load characteristics and the impact behaviours of reinforced concrete beams. Various characteristic values and their relationships are investigated such as the collision energy, the impact force duration, the energy absorbed by the beams and the beam response values. Also the bending performance of the reinforced concrete beams against perpendicular impact is evaluated.

An equation is proposed to estimate the maximum displacement of the beam based on the collision energy and the static ultimate bending strength. The validity of the proposed equation is confirmed by comparison with experimental results obtained by other researchers as well as numerical results obtained by FEM simulations. The proposed equation allows for a performance based design of the structure accounting for the actual deformation due to the expected impact action.

1 Introduction

Many mountainous areas in Japan present severe risks due to natural hazards as rockfall, frequent earthquakes, landslides and avalanches. About 70% of the land has a steep slope and is exposed to frequent rain or snow. Protection measures against rockfall are among the most important mea-

asures in preventing incidents, as the one illustrated in Fig. 1. Therefore, many protective structures have been constructed in mountainous areas (Masuya, 2005; Japan Road Association, 2000; Japan Railway Civil Engineering Association, 1978). The dynamic behavior of these structures under impact is generally very complex and closely related to the type of structure and the characteristic of material used. Furthermore, there are still difficulties in the design of the protective structures because many problems concerning the structural impact behavior and dynamic material properties of concrete, steel and of the sand cushion layer are unsolved yet. The subcommittee of impact problems of JSCE (2004) had therefore designated the examination of impact experimental and analysis methods as one of the priorities for standardization. The committee aimed for proposing a general impact test and measurement method and for showing the efficiency of numerical methods to reproduce the dynamic behavior of the structures.

Delhomme et al. (2005) performed impact experiments of a rockfall protection structure with a special structural energy dissipating system. Schellenberg (2007, 2009) showed a physical numerical model to express the interaction between a rockfall and the structure based on experiments. The present study provides experimental data concerning the dynamic behavior of protection structures to a higher level of damage. Several impact experiments have primarily been performed to study the dynamic behavior of structural members such as reinforced concrete beams. The experiments clarified the fundamental knowledge about experimental and measuring methods (Yamamoto et al., 2001; Nakata et al., 2002; Kishi et al., 2003; Tachibana et al., 2006). The final purpose of this study is to establish a methodology for the performance based design of structures (Subcommittee concerning performance based design of structures against impact action of JSCE, 2007).



Correspondence to: H. Masuya
(masuya@kenroku.kanazawa-u.ac.jp)



Fig. 1. Rockfall event on road N364, Kaga, December 2004.

Rock sheds are some of the protection structures subjected to impacts. Their roofs are made of either slab or beam structures. Generally, a layer of cushion material is used as shock absorber on top of the roof. As a result, compared with other dynamic actions, rockfall is in many cases a slow impact. Therefore, for rock sheds bending failure of the beams becomes dominant in most of the cases. For the prestressed concrete rock sheds, Masuya and Yamamoto (1999) showed design load factors for the expected limit states including bending failure. Sonoda (1999) showed the ultimate limit states of rock sheds and proposed a design method by means of a simple motion model expressing the bending failure.

In this research the impact behaviours of a reinforced concrete beam was studied evaluated for such bending failures.

Experiments on reinforced concrete beams were performed with the purpose of collecting fundamental data to establish a performance based design method for protection structures under impact loading. The characteristics of reinforced concrete beams under impact loading are shown. Further, it is suggested to an use of evaluation method predicting the maximum beam displacements based on the velocity of the impacting weight and the static ultimate bending capacity of the reinforced concrete beam.

2 Impact experiments

2.1 Specimen

Several series of impact tests were carried out using various reinforced concrete beams with shear reinforcement. Details of the beams and the reinforcement arrangement are shown in Fig. 2. Table 1 shows the design values of the different specimen.

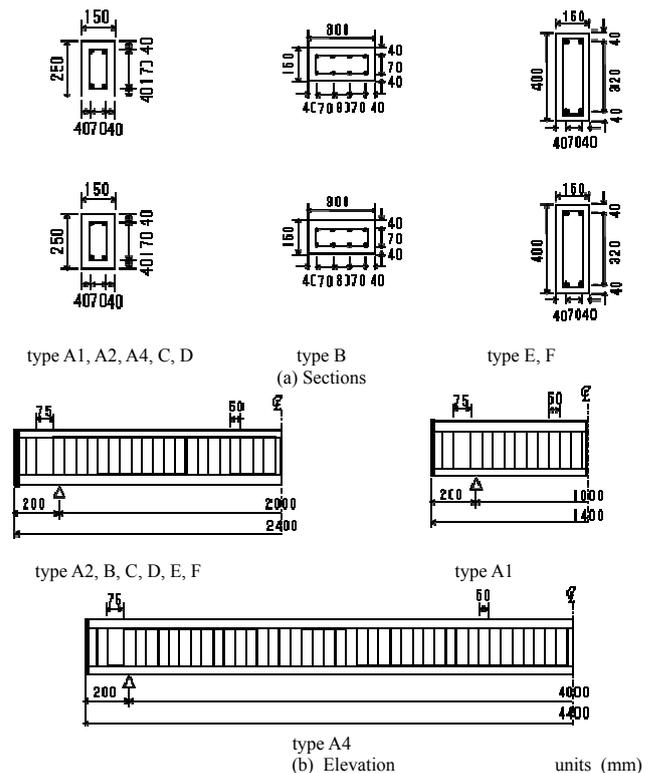


Fig. 2. Details of reinforced concrete beams.

All beams have rectangular sections with the main reinforcement arranged at the top and bottom sides and a shear reinforcement of 6-mm diameter (D6). The main reinforcement is welded to steel plates at the beam ends. The beam types A, C and D have the same sections with a width of 150 mm and a height of 250 mm. For types A1, A2 and A4, the span length is 1000 mm, 2000 mm and 4000 mm, respectively. For the beams type A, B and E, the diameter of the main reinforcement is 13 mm (D13). Diameter bars of 16 mm (D16) are used for type C and diameter 10 mm (D10) for types D and F.

The design strength of concrete is 24 MPa. The yield stress of the reinforcement is 345 MPa for the bending bars and 295 MPa for the stirrups, respectively. The static ultimate bending capacities P_u of the beam types B, F and A2 are comparable, while bending capacities of the beam types C and E are larger and the one of type D is smaller. The ultimate shear capacity V_u in all beams is larger than the ratio of capacity ($\gamma = (V_u/P_u) > 1$). Namely, the bending failure is preceding the shear failure for static load in all cases.

2.2 Test setup

Figure 3 shows the apparatus used for the falling weight impact experiments. The reinforced concrete beams are impacted by a steel weight, which is dropped from a specific height. The weight used in the experiments have a curved

Table 1. Design values of reinforced concrete beams.

Beam type	Width x height x span (m)	Diameter of bending reinforcement	Ultimate bending capacity P_u (kN)	Ultimate shear capacity V_u (kN)	Ratio of capacities $\gamma = (V_u/P_u)$	Bending stiffness EI_u (kN m ²)	Natural period T_0 (ms)
A1	0.15×0.25×1	D13	66.7	91.1	1.4	5729	2.5
A2	0.15×0.25×2	D13	33.3	91.1	2.7	5729	10.0
A4	0.15×0.25×4	D13	16.7	91.1	5.5	5729	40.1
B	0.30×0.15×2	D13	31.8	65.9	2.1	2412	16.9
C	0.15×0.25×2	D16	50.3	94.8	1.9	6088	9.7
D	0.15×0.25×2	D10	20.2	87.1	4.3	5342	10.4
E	0.15×0.40×2	D13	59.5	145.6	2.4	22 900	6.3
F	0.15×0.40×2	D10	34.9	140.6	4.0	21 590	6.5

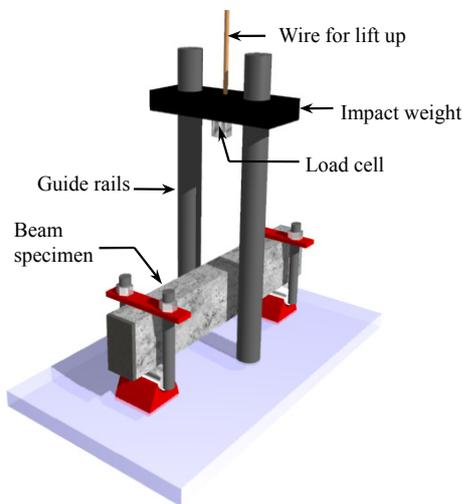


Fig. 3. Apparatus used for experiments.

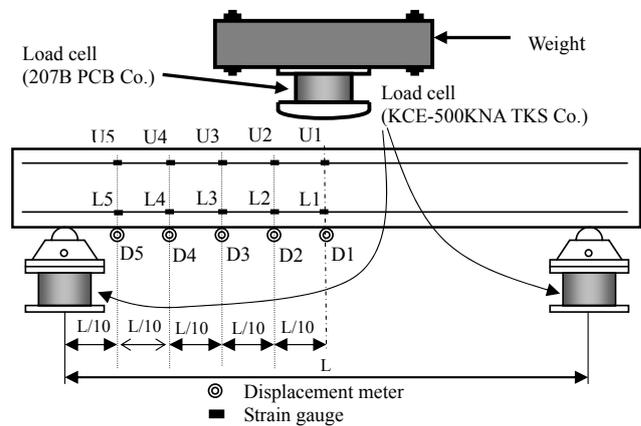


Fig. 4. Measurement items.

contact surface with a length of 565 mm, a radius of 75 mm and masses of 150 kg, 300 kg or 450 kg. The weights fall along two guiding rails. Special tie-down steel frames were installed on both supports preventing the beam from bouncing off the supports. Measured items were the impact force, the reaction forces at the supports, displacements of the beam and strains in the reinforcement. Measurements and their positions are shown in the Fig. 4. All output data was recorded with a rate of 20 kHz by means of a digital recorder (DR-M3 TEAC Co.).

Table 2 summarizes the conducted impact experiments considered in this paper. Two series of experiments were performed for specimen of type A2 with different combinations of impact mass and velocity. One series is performed varying the momentum and the other series varying the kinetic energy. For the specimen other than type A2, tests were performed under constant conditions in which the mass is 300 kg and the impact velocity is 5 m/s.

3 Experimental results

3.1 Characteristic values of impact

Figure 5 shows the time response of impact force, impact force-displacement curve and characteristic values resulted from those relations:

- Impulse I_p : integration of force-time curve.
- The absorbed energy E_p : integration of force-displacement curve.
- The mean impact force P_m : impulse I_p divided by duration of impact force T_d .

The results of the impact experiments (Table 3) are correlated with the energy consumed by the deformation of the beams. For the experiments Nos. 10–21 average values of several experiments are shown.

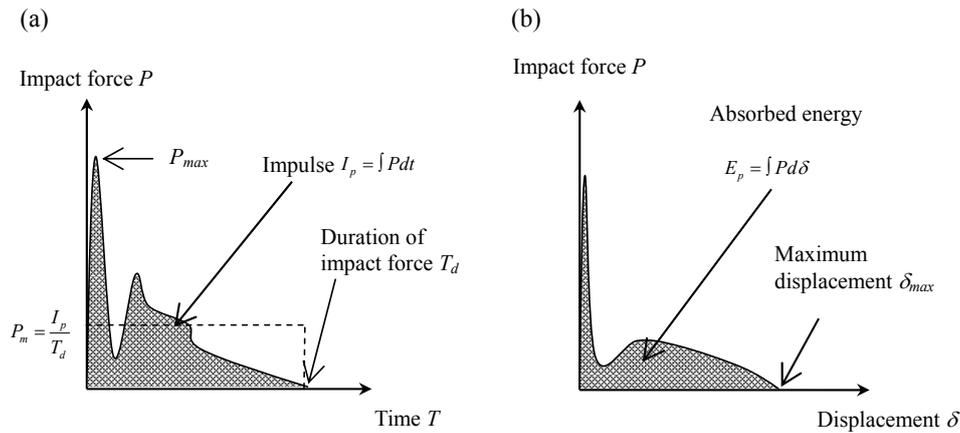


Fig. 5. Characteristic values. (a) Time response of impact force. (b) Force-displacement curve.

Table 2. Overview of impact tests.

No.	Specimen	Falling weight <i>m</i> (kg)	Impact velocity <i>V_{col}</i> (m/s)	Kinetic energy <i>E_{col}</i> (J)	Momentum <i>M_{col}</i> (N s)	No. of beams
1	A2	150	3.5	900	520	1
2	A2	300	2.4	900	735	1
3	A2	450	2	900	900	1
4	A2	150	4.9	1800	735	1
5	A2	300	3.5	1800	1039	1
6	A2	450	2.8	1800	1273	1
7	A2	150	6	2700	900	1
8	A2	300	4.2	2700	1273	1
9	A2	450	3.5	2700	1559	1
10	A2	300	1	150	300	1
11	A2	300	2	600	600	2
12	A2	300	3	1350	900	2
13	A2	300	4	2400	1200	2
14	A2	300	5	3750	1500	3
15	A1	300	5	3750	1500	4
16	A4	300	5	3750	1500	3
17	B	300	5	3750	1500	2
18	C	300	5	3750	1500	2
19	D	300	5	3750	1500	2
20	E	300	5	3750	1500	2
21	F	300	5	3750	1500	2

Table 3. Experimental results.

No.	Maximum impact force <i>P_{max}</i> (kN)	Impulse <i>I_p</i> (N s)	Duration time of impact force <i>T_d</i> (ms)	Mean impact force <i>P_m</i> (kN)	Absorbed energy <i>E_p</i> (J)	Maximum displacement <i>δ_{max}</i> (mm)
1	320.5	945.3	23.9	39.6	684.9	13.6
2	293.4	1240.3	25.4	48.9	836.4	25.4
3	245.3	1376.4	28.3	48.7	886.9	37.0
4	453.4	1096.4	26.7	41.1	1594.0	16.3
5	416.5	1459.9	34.0	43.0	1792.3	31.6
6	345.6	1798.3	37.7	47.8	1684.1	43.7
7	572.8	1365.7	33.9	40.3	1709.3	17.9
8	513.3	1896.6	42.4	44.7	2058.6	33.3
9	444.6	2199.4	47.5	46.3	2681.8	48.4
10	65.4	674.5	25.9	26.1	155.6	4.5
11	253.2	796.1	24.5	32.6	472.6	12.6
12	426.2	1277.0	33.3	38.3	1217.7	26.9
13	489.3	1525.3	37.7	40.5	2512.3	41.4
14	466.2	1940.2	41.6	46.7	3072.4	58.3
15	434.0	1976.5	18.6	106.4	3103.3	24.1
16	451.5	1851.2	105.6	17.5	2538.7	114.9
17	667.1	2039.7	57.8	35.4	3338.3	77.0
18	650.3	1988.4	32.9	60.6	2847.5	42.4
19	638.7	1906.7	63.0	30.3	3735.1	94.0
20	742.2	1830.0	25.3	72.5	2518.0	29.1
21	663.5	1655.6	33.8	49.0	2043.2	43.9

Note: No. 10 to No. 21 show average values.



Fig. 6. Crack pattern for test No. 14 (type A2, beam *m*=300 kg, *V_{col}*=5 m/s).

Figure 6 shows the crack pattern from a beam of type A2 after the impact a mass of 300 kg and a velocity of 5 m/s. It is a typical crack pattern for bending failure with small concrete fragmentation at the impact position.

3.2 Impulse and duration of impact force

Figure 7a shows the impulse *I_p* in relation to the ultimate bending strength *P_u* for experiments with a constant momentum at the time of collision of 1500 Ns. The impulse are about 2000 Ns and do not vary with the type of the beams. Therefore, it can be expected that the impulse depends on the momentum at the time of collision. Figure 7b shows the relation between the momentum of the weight and the impulse. This relationship can be expressed with the following

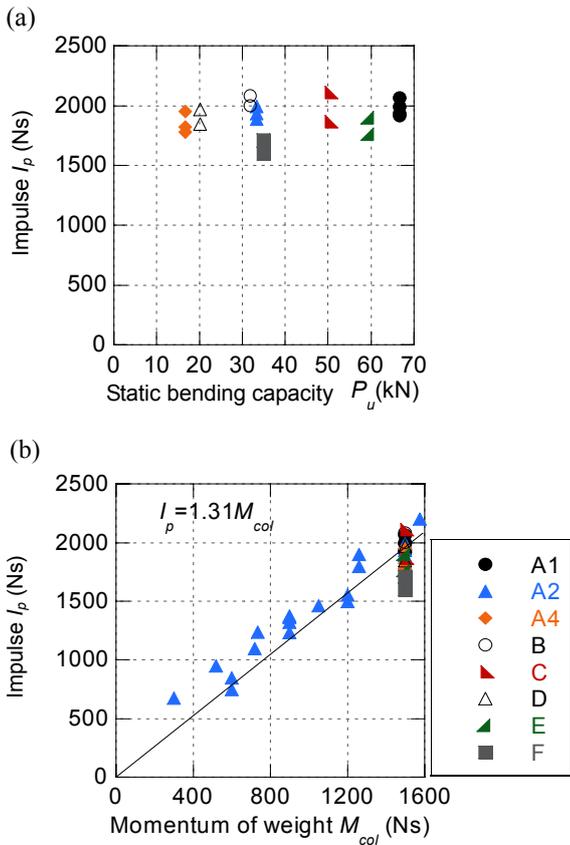


Fig. 7. Relationship between static bending capacity, momentum of weight and impulse. (a) Static bending capacity. (b) Momentum of weight.

equation.

$$I_p = 1.31 M_{col}. \tag{1}$$

Since rebounds were observed in all experiments, it is supposed that the value 1.31 expresses this effect. The physical amount of impulse I_p was 31% higher than the initial momentum of weight M_{col} . Therefore, the weight obtains an upward vertical velocity.

Figure 8a shows the impact force duration T_d in relation to the ultimate bending capacity of the specimen for the experiments with a momentum at the time of collision of 1500 Ns. A tendency is observed that the impact force duration T_d is decreasing when the static ultimate bending capacity is increasing. The displacement had reached the plastic range in all specimens. It was also revealed that the impact force duration is proportional to the momentum of weight at the time of collision. Hence, the impact force duration is proportional to the ratio of the momentum of the weight divided by the static ultimate bending capacity M_{col}/P_u shown in Fig. 8b. The graph can be expressed with the following equation.

$$T_d = 1.06 M_{col} / P_u. \tag{2}$$

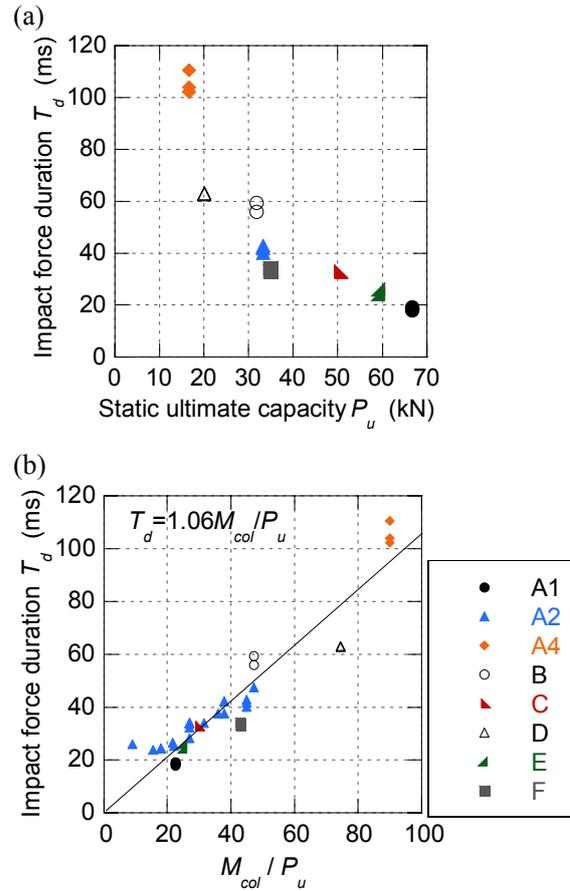


Fig. 8. Relationship between the duration of impact force and static ultimate bending capacity, the ratio of the momentum of the weight at the time of collision. (a) Static ultimate bending capacity. (b) Ratio of momentum of weight to static ultimate bending capacity.

It is noted that this equation is not valid for smaller impact intensities where the beam remains in the elastic range and no plastic deformations occur.

3.3 Maximum displacement of the beam

Figure 9 shows the time response of the displacement at the midspan for the case of a beam type A2 impacted by a mass of weight of 300 kg and a velocity of $V_{col}=5$ m/s. Large plastic strains are observed in the main reinforcement that resulted in large remaining displacements.

Figure 10 shows the relationship between the mean impact force P_m and the maximum displacement δ_{max} at midspan. In the case of an impact energy of $E_{col}=3750$ J, it is observed that the mean impact force P_m decreases with increasing maximum displacements in an inverse proportion. The two lines shown in Fig. 10 indicate the approximation curve for the impact with energies $E_{col}=3750$ and 1800 J. Thus, the

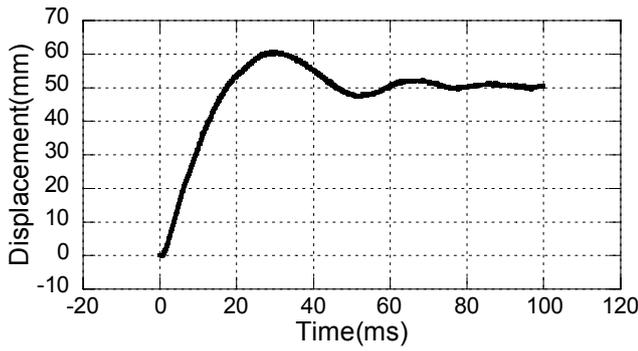


Fig. 9. Time response of the displacement at midspan for test No. 14 (type A2, $m=300$ kg, $V_{col}=5$ m/s).

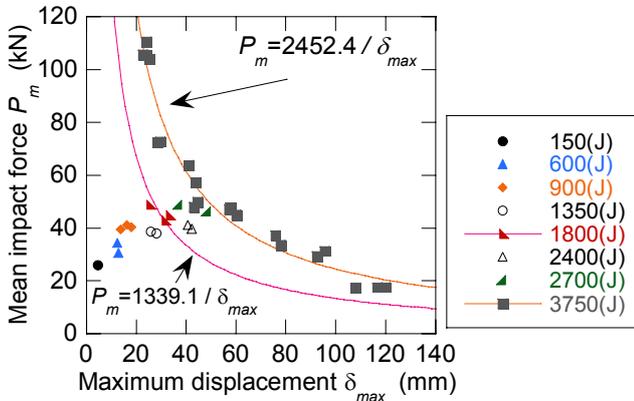


Fig. 10. Mean impact force and maximum displacement at midspan.

mean impact force is expressed with the following equation.

$$P_m = \alpha \frac{1}{\delta_{max}} \tag{3}$$

where α is a proportionality constant. Based on the results of 20 experiments for a kinetic energy of 3750 J (shown in Table 2, from No 14 to 21) α is found as 2452.

In the case of other impact energies from very few experimental results, we can observe that this relation is inverse proportional. The proportionality constant α in Eq. (3) has tendency to increase, for increasing impact energy E_{col} . Therefore, a constant of proportionality β for the impact energy E_{col} is assumed as shown in Eq. (4).

$$\alpha = \beta E_{col} \tag{4}$$

From Eqs. (3) and (4), the maximum displacement δ_{max} can be expressed by the Eq. (5).

$$\delta_{max} = \beta \frac{E_{col}}{P_m} \tag{5}$$

The maximum displacement is proportional to the impact energy E_{col} and is inverse proportional to the mean impact

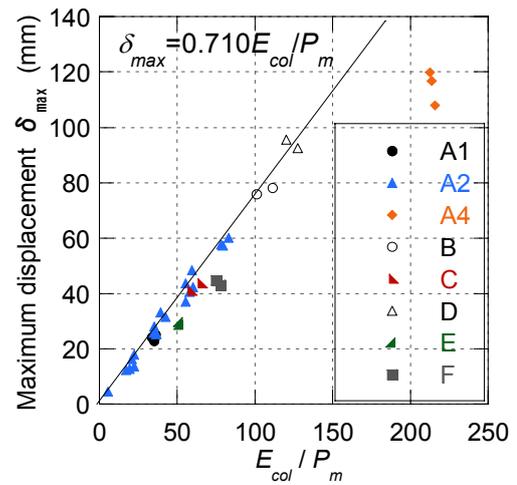


Fig. 11. Maximum displacements depending on E_{col}/P_u .

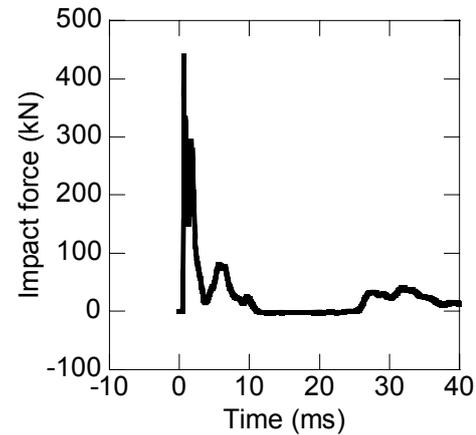


Fig. 12. Time response of impact force for test No. 16 (type A4, $m=300$ kg, $V_{col}=5$ m/s)

force P_m . Figure 11 shows the relation between the maximum displacement δ_{max} and the ratio impact energy to mean impact force E_{col}/P_m for each a type of all reinforced concrete beam. The maximum displacement δ_{max} is proportional to the ratio of impact energy to mean impact force E_{col}/P_m for most of the beams, excepted for the beam type A4, where the maximum displacement is slightly smaller.

Figure 12 shows the time response of the impact force for test No. 16 (beam type A4, impact velocity $V_{col}=5$ m/s and mass=300 kg). The initial impact occurs within 10 ms. After that, the impacting mass rebounds and no forces are transmitted from 10 ms to 25 ms.

The natural period of beam type A4 is about 40 ms. Therefore, the ratio of initial contact time to natural period T_d/T_0 is about 0.25. For the other experiments, the ratios are in the range of 2.4 to 5.2. Here, T_0 is the natural period of the beam shown in Table 1, T_d is the impact force duration, which was directly determined from time response as shown in Fig. 5 or

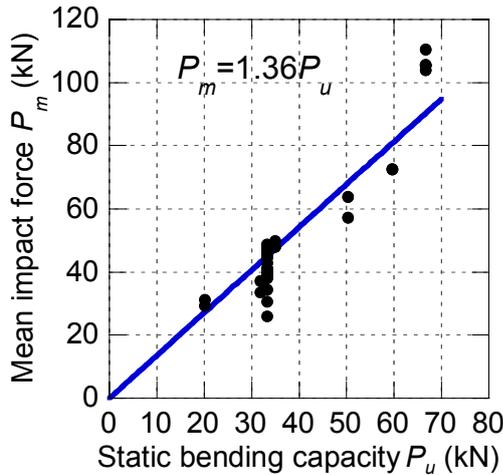


Fig. 13. Relationship between the mean impact force and the static ultimate bending capacity.

12. It can be considered that the influence of the duration of impact on the maximum deflection for the beam type A4 is small.

We excluded the beam type A4 shown in Fig. 11 for the approximation equation using the method of least squares. The maximum displacement δ_{max} of the reinforced concrete beams is expressed with following equation.

$$\delta_{max} = 0.710 \frac{E_{col}}{P_m} \tag{6}$$

Here, the correlation coefficient R^2 is 0.962 and the duration of impact T_d used to calculate the mean impact force P_m is the duration of the first impact until rebound.

On the other hand, the mean force P_m is the impulse divided by the duration of impact force. In this study, the utilization of the mean force P_m is possible, due to the measurements of the impact force. However, it is generally difficult to predict this value P_m . The ultimate bending strength P_u is the typical characteristic value for a reinforced concrete beam. If it is possible to use P_u instead of P_m , the estimation of dynamic behavior becomes easily and it gives significant benefit towards a performance based design of structure under impact. There is a positive correlation between the mean impact force P_m and the static ultimate bending capacity P_u from Eqs. (1) and (2). Here, we assume an approximation expressed with the following equation visualized in Fig. 13.

$$P_m = 1.36 P_u. \tag{7}$$

From Eqs. (6) and (7), the following equation is drawn.

$$\delta_{max} = 0.522 E_{col} / P_u \tag{8}$$

Figure 14 shows the relationship between the maximum displacement δ_{max} and the ratio kinetic energy to ultimate bending strength E_{col} / P_u , for which except for beam type A4,

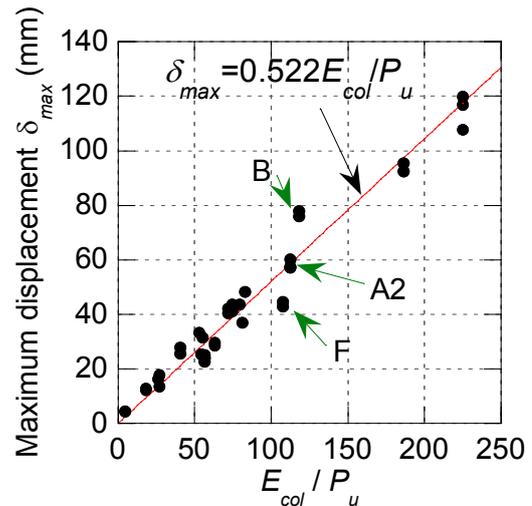


Fig. 14. Relationship between the ratio kinetic energy to ultimate bending capacity E_{col} / P_u and maximum displacement δ_{max} .


the collision velocity is 5 m/s and the impact mass is 300 kg. It becomes clear that the maximum displacement δ_{max} of the reinforced concrete beam can be calculated by the kinetic energy of the falling weight E_{col} and the static ultimate bending capacity P_u . The maximum displacement of the beam types A2, B and F under same impact conditions ($m=300$ kg and $V=5$ m/s) are also shown in Fig. 14. It is seen that the maximum displacement of the beam type A2 suits well with the estimated Eq. (8), and that the maximum displacements of the beam types B and F slightly deviate from Eq. (8). Nevertheless, the static ultimate bending capacities of the three beams are almost similar. The bending stiffness EI of the three beams varies largely and they influence the absorbed energy and the maximum displacement. It is noted that the Eq. (8) is valid under the condition of the ratio initial contact time to natural period $T_d / T_0 \geq 2.4$.

3.4 Verification of results

In order to verify the proposed equation, results are compared with other experimental research (Kishi et al., 2000) and numerical results (Tachibana, 2007). The accuracy of the FEM analysis was evaluated by comparison with experimental results (Masuya et al., 2007). Figure 15 shows the details of the reinforced concrete beams used in the comparison, and Table 4 summarizes the impact conditions and the maximum displacements. The concrete design strength is 24.0 MPa, the yield stress of the main reinforcement is 345 MPa and the yield stress of the shear reinforcement is 295 MPa. The diameter of the shear reinforcement is 6 mm for the beam type G and 10 mm for the beam type H. The ultimate bending capacity is 49.0 kN for the beam type G and 84.9 kN for the beam type H. An impact mass of 300 kg is used for all experiments.

Table 4. Impact conditions and maximum displacements.

Type	Diameter of bending reinforcement	Mass of weight	Impact velocity	Kinetic energy of weight at impact	Ultimate bending capacity	Maximum displacement
		M (kg)	V_{col} (m/s)	E_{col} (J)	P_u (kN)	δ_{max} (mm)
G-1	D19	300	5.0	3750	49.0	45.8
G-2	D19	300	6.0	5400	49.0	60.9
H-1	D22	500	3.13	2450	84.9	20.5
H-2	D22	500	4.20	4410	84.9	33.2
G-2(FEM)	D19	300	6.0	5400	49.0	60.6
H-2(FEM)	D22	500	4.20	4410	84.9	37.7
A2(FEM)	D13	300	5.0	3750	33.3	58.9

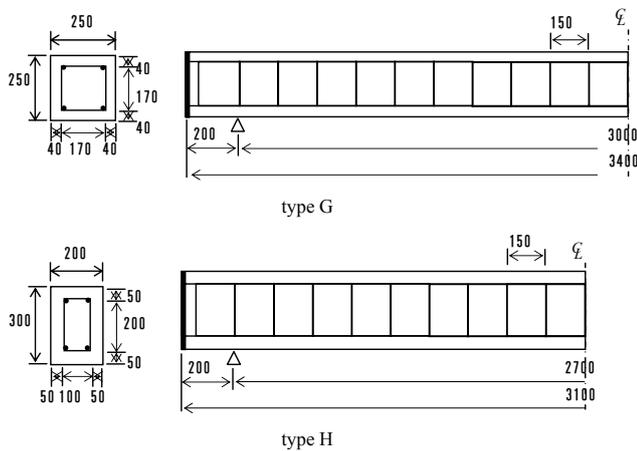**Fig. 15.** Details of reinforced concrete beams.

Numerical analyses by FEM were carried out for the beam types G-2, H-1 and A2, shown in Table 1. The impact behavior of the reinforced concrete beams was analysed using the finite element code ADINA (Automatic Dynamic Incremental Nonlinear Analysis) (Bathe, 1996). Figure 16 shows the finite element model used for beam type A2.

Drucker-Prager yield criterion is used for the material model of concrete. A bilinear model is used for steel reinforcement, where 0.4% of the Young modulus E_s is used for the plastic hardening H' .

Strain rate effects for concrete and steel are considered by means of a DIF (Dynamic Increase Factor). The DIF values for tensile and compressive strength for concrete and yield strength of steel reinforcement are $DIF_{ct}=1.2$, $DIF_{cc}=1.0$ and $DIF_s=1.2$, respectively.

These values are taken from research that aimed predicting the dynamic failures of reinforced concrete beams by means of various numerical methods (Kishi et al., 2008; Subcommittee of Impact Problems, 2004).

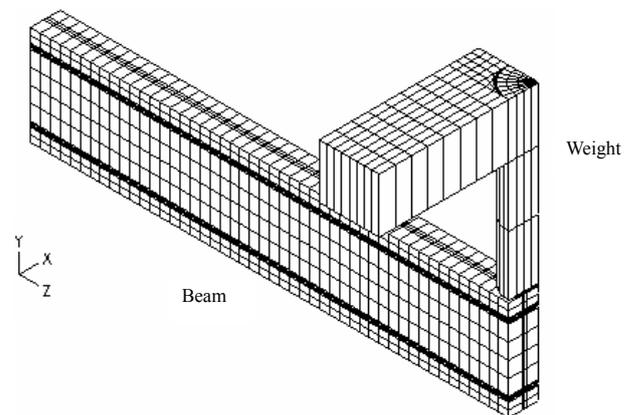
**Fig. 16.** Finite element model of quarter part of the beam and the weight.

Figure 17 shows the relation between these maximum displacements and impact energy divided by the static ultimate bending capacity with the proposed equation. The result from this equation is in good agreement with the additional experimental results and analytical results.

Therefore, it is considered that the proposed equation can be applied to estimate the maximum displacements of the reinforced concrete beams subjected to slow velocity impacts, which reach the inelastic range.

3.5 Applicability for a performance based design

Performance based design allows for satisfying performance requirements of structures without the restraint from the traditional design regulations. The impact loading is generally the most important action on protection structures such as rock sheds. Although rockfall is an accidental event for general structures such as bridges, it can be not considered as an accidental action for protection structures against rockfalls since protection of people from rockfalls is the

Table 5. The levels of impact action and the performance criterions of a protection structure or a structural member.

Impact action	Explanation by occurrence frequency	Damage	Safety	Serviceability	Repair
Level 1	The action corresponding to the maximum energy with the occurrence expected to be once or twice during several decades or the design working period of the road.	No damage	Safe to traffic vehicles and passing persons	No obstacle	No need
Level 2	The action corresponding to the maximum energy with the occurrence expected to be within 100 years.	Damage is limited within an allowable range.	Safe to traffic vehicles and passing persons	No obstacle	Small-scale repair
Level 3	The action corresponding to the largest energy with the possibility of occurrence by strong earthquake etc.	There is no fatal damage.	Safe to passing persons	Traffic restriction	Repair or reinforcement

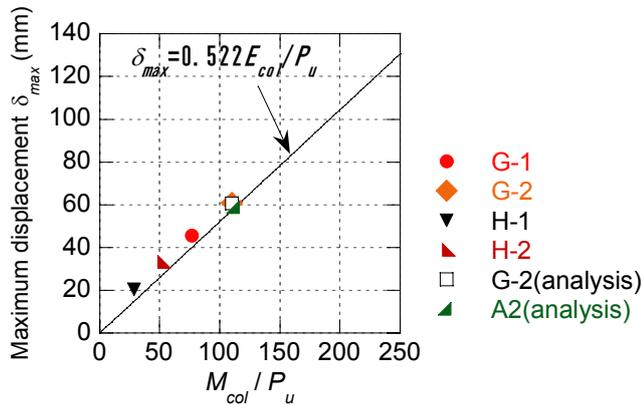


Fig. 17. Proposed equation and other results.

original purpose of the structure. Therefore, dealing with the impact load as an identified variable action or as an action based on a certain scenario seems more appropriate rather than as an accidental action. Table 5 shows exemplary levels of impact action and performance criterions of a protection structure. The relationships between the impact action levels and the performance criterions are generally related to the importance of the planed protection structure. It is consequently thought that the classification of the loads according to action levels is required for a performance based design.

Although the outcome of this research can not be directly applied to all types of protection structures, it shows a considerable concept to treat the flexural deflections of structures due to impact loading. Based on the action level shown in Table 5, the collision energy can be specified and the maximum displacement of the beam can be determined by Eq. (8). Consequently, it can be assessed whether the resulting damage of the beam satisfies the performance criterions shown in Table 5. Subsequently, it can be verified whether adjustments in the design are necessary. In a similar manner, the max-

imum displacement of the beam can also be evaluated for other impact position and other support condition also can be evaluated in similar manner.

It is expected that the method shown here can be also applied to other protection structures in the future. For that scope, further experimental data is needed, with and without shock absorbing layers. This method can not be applied to cases where shear failure occurs. It is also necessary to have more research regarding the analysis technique such as Finite Element Method with high reproducibility (Masuya et al., 2006; Kishi et al., 2008), which would allow for further parameter studies and enhancement of the proposed equations.

4 Conclusions

Series of impact experiments were carried out aiming to obtain fundamental data to establish a performance based design of reinforced concrete beams with preceding bending failure (the margin degree of static shear capacity to static bending capacity $\alpha \geq 1$). The reinforcement, sectional dimensions and span lengths of the reinforced concrete beams were varied. The static ultimate bending capacity of these reinforced concrete beams ranges from 16.7 kN to 66.7 kN. Also, the impact energy varies from 150 J to 5400 J based on the variation of mass and impact velocity. From the impact experiments various results and their relations were registered for the different beam types. Also the estimation of bending displacement of reinforced concrete beam due to impact has been investigated.

The results obtained by this study are concluded as follows:

1. The impulse resulting from the impact is proportional to the momentum of the impacting mass and the impact force duration, and is directly proportional to the momentum of the impacting mass divided by the

static ultimate bending capacity M_{col}/P_u with respect to all kind of reinforced concrete beams.

2. The maximum displacement is inverse proportional to the mean impact force. The maximum displacement is in proportional relation to the value of the mean impact force divided by impact energy E_{col}/P_m .
3. The relation between the mean impact force and the static ultimate bending capacity is shown. It is clear that the maximum displacement of the beam is almost proportional to the impact energy divided by the static ultimate bending capacity E_{col}/P_u .
4. It is determined that the estimated equation with respect to the maximum displacement of reinforced concrete beams can be calculated by the kinetic energy and velocity of the impacting mass and the static ultimate bending capacity. The verification of the proposed equation was made by comparisons with other experimental results and results from finite element method. It has been shown that the approach and the concept to estimate the maximum bending displacement of the structure under impact, allows for a performance based design of protection structures.

Acknowledgements. K. Schellenberg, C. di Prisco and anonymous referees made important contributions to the article. Nihon Samicon Co., Ltd provided a number of concrete specimens in this study. Many members of the subcommittee concerning performance based design of structures against impact action of JSCE gave the authors valuable comments and suggestions on various occasions. The authors would like to express sincere gratitude.

Edited by: K. Schellenberg

Reviewed by: C. di Prisco and four other anonymous referees

References

- Bathe, K. J.: Finite Element Procedures, Prentice Hall, 1996.
- Delhomme, F., Mommessin, M., Mougouin J.-P., and Perrotin P.: Behavior of a structurally dissipating rock-shed: experimental analysis and study of punching effects, *Int. J. Solids Struct.*, 42(14), 4203–4219, 2005.
- Japan road association: Handbook of preventatives against rock-falls, Japan road association, Japan Road Association, 2000 (in Japanese).
- Japan Railway Civil Engineering Association: Manual for preventive structures against rock falls, Japan Railway Civil Engineering Association, 1978 (in Japanese).
- Kishi, N. and Miakmi, H.: An empirical impact resistant design formula of RC beams with statically bending failure mode, *Japan Society of Civil Engineers, J. Struct. Earthq. Eng.*, No. 647/I-51, 177–190, 2000.
- Kishi, N., Ando, T., Imoto, K., Kasai, Y., Katuki, S., Kambayashi, A., and Masuya, H.: Round-robin analysis on impact behaviour of RC beam subjected to a falling-weight impact force, *Japan Society of Civil Engineers, J. Struct. Eng.*, 49A, 1299–1310, 2003.
- Kishi, N., Ohno, O., Imoto, K., Ishida, M., Kasai, Y., Kanbayashi, A., and Masuya, H.: Round robin pre/post analysis of RC beam under falling-weight impact, *Proceedings of International Symposium on Structures under Earthquake, Impact, and Blast Loading (IB'08)*, 217–224, 2008.
- Kishi, N.: Numerical impact response analysis of rockfall protection galleries, *Struct. Eng. Int.*, 19, 301–320, 2009.
- Nakata, Y., Masuya, H., and Nishimura, Y.: Study on characteristic of impact behavior of reinforced concrete beam from the view of momentum and kinetic energy of collision body, *Japan Society of Civil Engineers, J. Struct. Eng.*, 48A, 1493–1503, 2002.
- Masuya, H.: Impact problem concerning rock falls and research activities of related field in Japan, *Proc. of 6th Asia-Pacific Conference on shock & impact loads on structures*, CI-Premier Pte Ltd., 63–70, 2005.
- Masuya, H. and Tachibana, S.: Simulation of behavior of reinforced concrete beam under impact, in: *Proceedings of the 2nd international conference on design and analysis of protective structures against impact/impulsive/shock loads*, Organized by the Defence Science & Technology Agency of Singapore and Nanyang Technological University, 406–416, 2006.
- Masuya, H. and Yamamoto, M.: Load resistant factor of rock-sheds in heavy snow area, *Proceedings of the joint Japan-Swiss scientific seminar on impact load by rock falls and design of protection structures*, 121–128, 1999.
- Schellenberg, K., Volkwein, A., Roth, A., and Vogel, T.: Large-scale impact tests on rock fall galleries, *Proceedings of the 7th International Conference on Shock and Impact Loads on Structure*, CI-Premier Pte Ltd., 497–504, 2007.
- Schellenberg, K.: *On the Design of Rockfall Protection Galleries*, Südwestdeutsche Verlag für Hochschulschriften, p. 186, 2009.
- Sonoda, K.: Ultimate limit states of rockshed and design method, in: *Proceedings of the joint Japan-Swiss scientific seminar on impact load by rock falls and design of protection structures*, edited by: Masuya, H. (Kanazawa University) and Labiouse, V. (Swiss Federal Institute of Technology Lausanne), 129–136, 1999.
- Subcommittee of Impact Problems of JSCE: *Practical methods for impact test and analysis*, edited by: Kishi, N., Japan Society of Civil Engineers (JSCE), 2004.
- Subcommittee concerning performance based design of structures against impact action of JSCE: *Design method of structures under impact action by concept of performance based design*, edited by: Masuya, H., Japan Society of Civil Engineers (JSCE), *Structural Engineering Technical Series No. 52*, 2007.
- Tachibana, S.: Study on dynamic behavior and performance of reinforced concrete beams under impact, Doctor of Engineering thesis, Kanazawa University, Dissertation No. 2863, 2007.
- Tachibana, S., Masuya, H., and Nakamura, S.: Experimental study on the impact behavior and performance of reinforced concrete beam with some absorbing materials, *Proceedings of the 31st conference on our world in concrete & structures*, CI-Premier Pte Ltd., 387–398, 2006.
- Yamamoto, M., Masuya, H., Onda, S., Horie, T., and Kumagai, T.: A study on the impact test method and characteristics of behavior of reinforced concrete beam by a weight drop, *Japan Society of Civil Engineers, J. Struct. Eng.*, 47A, 1683–1694, 2001.